

## Nanoelectromechanical systems based on multi-walled nanotubes: nanothermometer, nanorelay, and nanoactuator

Andrey M. Popov<sup>\*,1</sup>, Elena Bichoutskaia<sup>\*\*,2</sup>, Yurii E. Lozovik<sup>\*\*\*,1</sup>, and Anton S. Kulish<sup>3</sup>

<sup>1</sup> Institute of Spectroscopy, Troitsk, Moscow region 142190, Russia

<sup>2</sup> University Chemical Laboratory, Lensfield Road, Cambridge CB2 1EW, UK

<sup>3</sup> Moscow Institute for Steel and Alloys, Leninskii prosp. 4, Moscow 117936, Russia

Received 10 October 2006, revised 1 January 2007, accepted 3 January 2007

Published online 23 May 2007

PACS 61.46.Fg, 85.85.+j, 87.80.Mj

We report on three new types of nanoelectromechanical systems based on carbon nanotubes: an electromechanical nanothermometer, a nanorelay and a nanomotor. The nanothermometer can be used for accurate temperature measurements in spatially localized regions with dimensions of several hundred nanometers. The nanorelay is a prototype of a memory cell, and the nanoactuator can be used for transformation of the forward force into the relative rotation of the walls. Relative motion of the walls in these nanosystems is defined by the shape of the interwall interaction energy surface. *Ab initio* and semi-empirical calculations have been used to estimate the operational characteristics and dimensions of these nanosystems.

© 2007 WILEY-VCH Verlag GmbH & Co. KGaA, Weinheim

### 1 Introduction

Unique properties of carbon nanotubes, such as free sliding and rotation of the walls and metallic conductivity, allow using the walls of nanotubes as movable elements and elements of electric circuit in nanoelectromechanical systems (NEMS). An example of such applications is a nanotube-based nanomotor which has been produced recently [1, 2]. A set of NEMS based on relative motion of the walls of nanotubes, such as a nanospring [3], a nanoswitch [4] and a gigahertz oscillator [5] have been suggested in the literature. A number of nanorelays with one electrode made of a carbon nanotube have also been considered [6–8]. A new type of NEMS in which the relative motion of the walls is controlled by the shape of the interwall interaction energy surface has been proposed in [9, 10] as a nanodrill, in [11] as a tension nanosensor and in [12, 13] as rotational nanobearings with fixed relative position of a sleeve and a shaft along the axis. In this paper, we propose three new NEMS of this type: an electromechanical nanothermometer, a nanorelay with all electrodes made of nanotubes, which can also be used as a memory cell, and a nanoactuator for transformation of forward force into relative rotation of the walls.

### 2 Methods of calculations

The density functional theory supercell code within the local density approximation (AIMPRO [14]) has been used to calculate the interwall interaction energy and the barriers to the relative sliding of the walls

\* Corresponding author: e-mail: popov@ttk.ru, Phone: +7 495 334 0881, Fax: +7 495 334 0886

\*\* e-mail: enb25@cam.ac.uk

\*\*\* e-mail: lozovik@isan.troitsk.ru

for the (5,5)@(10,10) and (6,6)@(11,11) double-walled carbon nanotubes (DWNTs). The details of the method can be found in [13, 15]. Within AIMPRO, the pseudowave functions are described by 4 atom-centered Gaussian functions per atom expanded in spherical harmonics up to  $l=1$ , with the second smallest exponent expanded to  $l=2$ . The supercell consists of 60 and 68 carbon atoms for the (5,5)@(10,10) and (6,6)@(11,11) DWNTs, respectively. The Brillouin Zone sampling has been performed using 18 special  $k$ -points in the direction of the nanotube axis. Non-local, norm-conserving pseudopotential and the standard Perdew–Wang exchange–correlation functional [16] have been used. Minima in the total energy are found using a conjugate gradient scheme to an accuracy of 1  $\mu\text{eV}/\text{atom}$ . Positions of all atoms in the isolated (5,5), (6,6), (10,10) and (11,11) walls have been optimized.

Structures of the caps of the nanotubes used as the electrodes of a nanorelay have been calculated using the Q-Chem 2.1 quantum chemistry package [17]. The 6–12 Lennard–Jones potential  $U = 4\varepsilon((\sigma/r)^{12} - (\sigma/r)^6)$  has been used for calculation of the interaction between the electrodes of a nanorelay. Parameters  $\sigma = 3.44 \text{ \AA}$  and  $\varepsilon = 2.62 \times 10^{-3} \text{ eV}$  [18] have been used for the interaction between carbon atoms, and  $\sigma = 2.039 \text{ \AA}$ ,  $\varepsilon = 0.14438 \text{ eV}$  [19] for the interaction between carbon and copper atoms.

### 3 Nanoelectromechanical systems

#### 3.1 Electromechanical nanothermometer

A new concept of an electromechanical nanothermometer is based on the interaction and relative motion of the walls of carbon nanotubes. Temperature measurements are carried out through the measurements of the electrical conductance of the walls as a function of their relative displacement. Relative position of the walls of a nanotube depends on and changes with the temperature due to the thermal vibrations of the walls. The probability of the relative displacement of the walls,  $p(q)$ , is defined by the energy of their interaction,  $U(q)$ , as  $p(q) \sim \exp(-U(q)/kT)$ . For a given temperature, the total conductance,  $G_{\text{tot}}(T)$ , can, therefore, be found as the expectation value of the conductance at a fixed position of the walls,  $G(q, T)$  [20].

$$G_{\text{tot}}(T) = \frac{\int_{-\infty}^{\infty} G(q, T) \exp(-U(q)/kT) dq}{\int_{-\infty}^{\infty} \exp(-U(q)/kT) dq}. \quad (1)$$

Equation (1) takes into account contributions from the thermal vibrations of the walls.

The working conditions for the electromechanical nanothermometer are the following:  $G(q, T)$  depends significantly on the coordinates  $q$  (condition A);  $G(q, T)$  depends weakly on the temperature  $T$  (condition B) (contributions from phenomena other than the thermal vibrations of the walls are insignificant); amplitude of the thermal vibrations is large enough to provide the main contribution to the temperature dependence of the total conductivity  $G_{\text{tot}}(T)$  (condition C); amplitude of the thermal vibrations is still small for the relative displacements of the walls to upset the normal operation of the system (condition D).

A model implementation of the nanothermometer is based on the (6,6)@(11,11) DWNT (Fig. 1). The conductance of the (6,6)@(11,11) DWNT depends significantly on the relative position of the walls in both telescopic and shuttle systems [21] and changes due to the thermal vibrations of the walls. Therefore, the condition A is fulfilled. Experimental studies of [22] show that the conductance of single-walled carbon nanotubes depends weakly on the temperature in the region of  $T > 50 \text{ K}$ . Theoretical studies of [23] conclude that for DWNTs with fixed walls it depends weakly on the temperature for  $T > 100 \text{ K}$ . Thus, the condition B is also satisfied in these temperature regions.

The dependence of both the interaction energy of the walls of a nanotube and the conductance on the displacement of the walls is uniquely determined by the symmetry of the (6,6)@(11,11) DWNT.  $U(q)$  and  $G(q)$  show some common features, for example, they have the same period of oscillation and the



**Fig. 1** Schematics of an electromechanical nanothermometer based on DWNT: A) a shuttle nanothermometer with the movable inner wall, B) a telescopic nanothermometer with the movable outer wall. 1 is the movable wall, 2 is the fixed wall with the attached electrodes 3.

extrema in both functions coincide. Moreover, the dependence of the interwall interaction energy and the conductance on the angle of relative rotation of the walls is negligible due to incompatibility of the rotational symmetries of the (6,6) and (11,11) walls.

In the absence of diffusion of the short wall, integration in Eq. (1) can be performed near the bottom of the potential well of the interwall interaction energy  $U(q)$ . This region can be interpolated as [24]

$$U(q') = U_1 + \frac{\pi \Delta U_q}{\delta_q^2} q'^2, \quad (2)$$

where  $U_1$  is the interwall interaction energy of the ground state,  $\Delta U_q$  is the energy barrier between the minima of  $U(q)$ ,  $\delta_q$  is the period of displacement of the walls between the minima, and  $q'$  is a displacement of the movable wall from the position which defines the ground state. For small values of  $q'$ ,  $G(q', T)$  can be interpolated as [24]

$$G(q') = G_1(T) (1 + \gamma q'^2), \quad (3)$$

where  $G_1$  is the conductivity of DWNT in the ground state. The value of  $\gamma$  for the overlap of the walls of 2.45 nm can be extracted from the Fig. 3 of [21] as  $\gamma \sim 850 \text{ \AA}^{-2}$ .


Substitution of (2) and (3) into (1) leads to the following expression for the dependence of the conductance of the nanothermometer on the temperature

$$G(T) = G_1(T) \left( 1 + \frac{\gamma \delta_q^2 kT}{\pi \Delta U_q} \right) = G_1(T) (1 + HT). \quad (4)$$

Here the energy barrier  $\Delta U_q$  for the (6,6)@(11,11) DWNT has been calculated *ab initio* and for the overlap of the walls of 2.45 nm it has the value of 1.96 eV. Therefore, for  $T = 300 \text{ K}$ , the value of  $HT$  in (1) is about 45 and this ensures the fulfillment of the condition  $C$ . For the condition  $D$  to be satisfied, the displacement of the shuttle as a result of diffusion has to be less than the distance between the electrode and the shuttle. The minimum length between the electrodes of the shuttle nanothermometer which operates during 100 years without a failure is estimated as 38 nm using the *ab initio* results [25] for the diffusion coefficient of the walls of (6,6)@(11,11) DWNT. The nanothermometer can be calibrated with the use of a thermocouple, and since the temperature measurement is based on conductance measurement, the same order of accuracy as in the case of thermocouple using can be achieved (for example, the accuracy of measurements at room temperature is about 0.1 K for copper-constantan and chromel-alumel thermocouples).

### 3.2 Nanorelay

The essential working condition for a nanosystem to operate as a relay is the presence of two minima in the interaction energy of its components (positions 'on' and 'off'), or so called bi-stability. A nanotube-

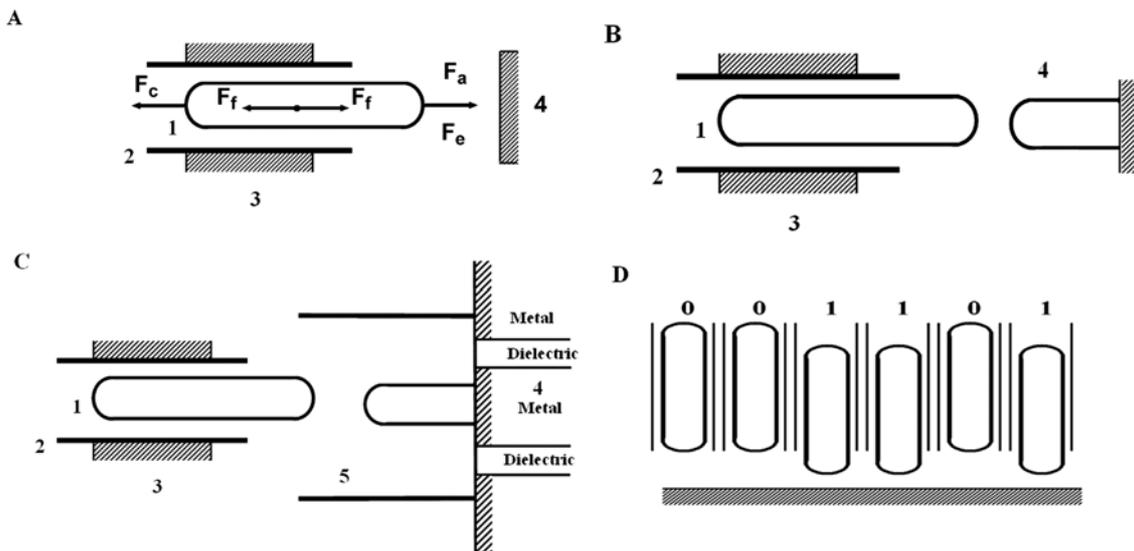


**Fig. 2** Schematics of memory cells based on DWNTs (in position ‘on’). 1 is the movable inner wall; 2 is the fixed outer wall; 3, 4 and 5 are the first, second and the control electrodes. A) a memory cell with a flat second electrode; B) an ‘all-carbon’ memory cell with a carbon nanotube attached to the second electrode; C) an ‘all-carbon’ memory cell with a control electrode made of a nanotube. D) shows an example of the storage produced from memory cells.

based nanorelay (Fig. 2A) has been recently proposed in [8]. Here we propose new schemes of nanorelays of this type (Fig. 2B, C). Their operation is fully determined by the the forces applied to the movable inner wall 1. These forces are the attraction force,  $F_a$ , of the Van der Waals interaction between the electrodes; the electrostatic force,  $F_e$ , between the electrodes 3 and 4 (Fig. 2A, B) or between the electrode 3 and the control electrode 5 (Fig. 2C); and the forces of the interwall interaction, such as the capillary force  $F_c$ , which retracts the inner wall, and the static friction force  $F_f$ .

For the (5,5)@(10,10) DWNT, the capillary force  $F_c$  is estimated in [13] as 0.625 nN. The results for calculations of the interaction between the electrodes are presented in Table 1. According to the *ab initio* [15] and semiempirical [12] calculations, the friction force  $F_f$  is approximately zero for DWNTs with incommensurate or/and chiral walls. If the condition for bi-stability,  $F_a > F_c$ , is satisfied then the nanorelay can be used as a memory cell of the external storage. If one of the electrodes of the nanorelay is made of a DWNT with incommensurate or chiral walls, the condition for bi-stability can only be achieved if the second electrode is flat (see Fig. 2A). An ‘all-carbon’ nanorelay with both electrodes made of carbon nanotubes is shown in Fig. 2B. In the case of small friction force  $F_f$ , this nanorelay is stable in position ‘on’ only if the voltage is applied. Therefore, it can be used as an easy-to-operate memory cell of the on-line storage (see Fig. 2D).

**Table 1** Characteristics of the interaction between the electrodes of the nanorelay:  $U_{\min}$  (in eV) is the minimum value of the interaction energy between the electrodes,  $R_{\min}$  (in Å) is the distance between the electrodes which corresponds to the minimum of the interaction energy;  $F_a^{\max}$  (in nN) is the maximum attraction force between the electrodes.

second electrode	$U_{\min}$	$R_{\min}$	$F_a^{\max}$
graphite	-0.914	3.153	0.683
copper	-35.69	1.879	42.32
(5,5) nanotube	-0.259	3.345	0.233

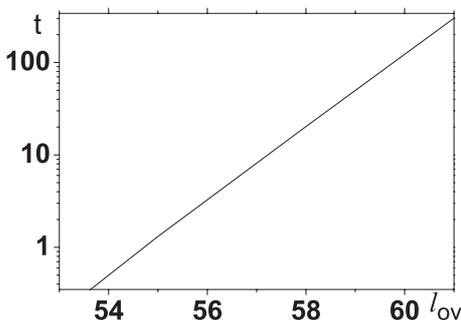

**Fig. 3** Dependence of the lifetime (in years) of the ‘all-carbon’ nanorelay in position ‘on’ on the overlap of the walls (in nm). The nanorelay contains the (5,5)@(10,10) DWNT as the first electrode and the (5,5) nanotube as the second electrode.

In the case of DWNTs with nonchiral commensurate walls, the friction force  $F_f$  is significant [12, 15]. For the (5,5)@(10,10) DWNT, the dependence of the force  $F_f$  on the overlap of the walls,  $l_{ov}$ , can be described as  $F_f = Al_{ov} \cos(2\pi l_{ov}/\delta_q)$ , where  $A = 0.01$  N/m [13]. The analysis of the balance of forces in ‘all-carbon’ nanorelay shows that for the critical overlap  $l_c = 4$  nm, the sum of the interwall static friction force and the attraction force of the Van der Waals interaction between the electrodes,  $F_f + F_a$  has to be greater than the capillary force  $F_c$ . If the overlap of the walls is greater than the critical value,  $l_{ov} > l_c$ , the nanorelay can be bi-stable.

The condition  $l_{ov} > l_c$  is not sufficient for the successful operation of the ‘all-carbon’ nanorelay as a memory cell of the external storage. The energy barrier between positions ‘on’ and ‘off’ can be, in principle, overcome as the result of the thermal diffusion of the inner wall 1. The probability of this is determined by the Arrhenius formula  $p = \Omega \exp(-\Delta U/kT)$ , where  $\Omega$  is the frequency multiplier. According to the molecular dynamics simulation of the reorientation of shells of the  $C_{60}@C_{240}$  nanoparticle [26], the frequency multiplier is about an order of magnitude greater than the frequency of small oscillations near the minimum of the intershell interaction energy. The dependence of the lifetime,  $t = p^{-1}$ , of the ‘all-carbon’ nanorelay in position ‘on’ on the overlap of the walls is shown on in Fig. 3.


For the case of a nanorelay with the control electrode made of a carbon nanotube (Fig. 2C), the electrostatic force  $F_e$  acting on the (5,5) movable wall has been calculated. The movable wall and control electrode, taken to be 3 nm, comprise the armatures of cylindrical capacitor. Assuming the friction force  $F_f$  is negligible, the voltage of the switching between positions ‘off’ and ‘on’ can be determined by the condition  $F_e > F_c$  and estimated to be about 6 V. In this case, the voltage needed to hold the nanorelay in position ‘on’ is about 4.8 V.

### 3.3 Nanoactuator

A nanoactuator has been designed for transformation of the forward force into the relative rotation of the walls. Schematic of the nanoactuator is shown in Fig. 4. The wall 1 of the nanotube is fixed making a stator. Relative position of the walls 2 and 3, which comprise a rotor, is also fixed. The walls 3 and 4 make up a bolt-nut pair which converts the motion driven by an axially directed force applied to the wall 4 into the rotation of the rotor. It has been shown in [27, 28] that the bolt-nut pair can be a DWNT with periodically positioned defects.

The first of the essential working conditions for the nanoactuator is defined by the motion of the walls 1 and 2, which constitute a rotational nanobearing. This condition states that the barrier to the rotation of the walls 1 and 2 has to be low and the barrier to the sliding axial motion of these walls has to be high. This condition is satisfied if both 1 and 2 are commensurate achiral walls with incompatible rotational symmetry [12, 13].

The second of the essential working conditions for the nanoactuator is defined by the motion of the walls 3 and 4, which constitute a bolt-nut pair. If a short impulse of the force directed along the axis is applied to the wall 4, this wall acquires the kinetic energy sufficient to overcome the barrier  $E_1$  to the

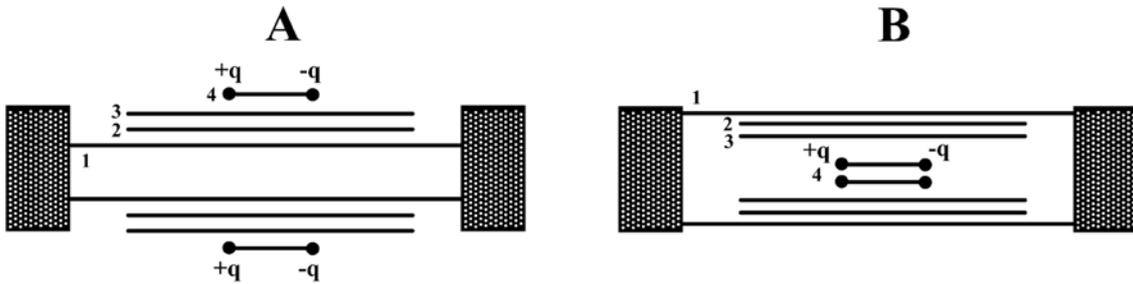

**Fig. 4** Schematics of a nanoactuator: A) a nanoactuator with the inner wall 1 as a stator, B) a nanoactuator with the outer wall 1 as a stator. The walls 1 and 2 comprise the rotational nanobearing, the walls 3 and 4 are the bolt-nut pair with the thread-like shape of the interwall interaction energy.

motion of the walls 3 and 4 along the line of the thread. However, the energy will not be large enough to overcome the barrier  $E_2$  to the motion of the walls 3 and 4 across the line of the thread, i.e.

$$\frac{MV^2 \sin^2 \chi}{2} > E_1, \quad \frac{MV^2 \cos^2 \chi}{2} < E_2, \quad (5)$$

where  $M$  and  $V$  are the mass and velocity of the wall 4, and  $\chi$  is the angle of the thread. The inequalities (5) are fulfilled if  $\cot^2 \chi < E_2/E_1 = \beta$  where  $\beta$  is the depth of the thread as given in [9, 10]. Evidently, if the angle  $\chi$  of the thread is greater than 45 degrees than the nanoactuator can operate with any depth of the thread. The charges on the edges of the wall 4 can be produced by chemical adsorption.

The conservation of the angular momentum of the nanoactuator gives the minimum length  $L_3^{\min}$  of the wall 3 for which the rotation at an angle  $\xi$  becomes possible

$$L_3^{\min} = \frac{L_4 R_4^2}{L_4 R_4^2 + \xi (R_2^3 + R_3^3) \sin \chi}, \quad (6)$$

here  $L_4$  is the length of the wall 4;  $R_2$ ,  $R_3$  and  $R_4$  are the radii of the walls 2, 3 and 4, respectively. The operation time of the proposed nanorelay and nanoactuator can be the same order of magnitude as oscillation period 10–100 ps of nanotube-based gigahertz oscillator [5].

#### 4 Conclusive remarks

We proposed three new nanotube-based NEMS: a nanothermometer, a nanorelay with ‘all-carbon’ electrodes and a nanoactuator. A considerable progress has been recently achieved in the nanotechnology techniques in the field of production of NEMS. A nanomanipulator can be now attached to MWNT in order to move individual walls [3], manipulation with nanotubes is routinely possible [29], the caps of the walls can be removed [30], nanotubes can be cut into pieces of desirable length [31], the techniques for unambiguous determination of chirality of the walls have been successfully demonstrated [32]. All these gives us a cause for the optimism that the proposed NEMS will be produced in the near future.

**Acknowledgement** EB is indebted to the Royal Society for a UK Relocation Fellowship. This work has been partially supported by the Russian Foundation of Basic Research (AMP, YEL and ASK, grants 05-02-17864 and 06-02-81036-Bel). We thank Dr. N. A. Besley for his help with calculation of structures of the nanotube caps.

#### References

- [1] A. M. Fennimore, T. D. Yuzvinsky, W. Q. Han, M. S. Fuhrer, J. Cumings, and A. Zettl, *Nature* **424**, 408 (2003).
- [2] B. Bourlon, D. C. Glatti, L. Forro, and A. Bachfold, *Nano Lett.* **4**, 709 (2004).
- [3] J. Cumings and A. Zettl, *Science* **289**, 602 (2000).

- [4] L. Forro, *Science* **289**, 5479 (2000).
- [5] Q. Zheng and Q. Jiang, *Phys. Rev. Lett.* **88**, 045503 (2002).
- [6] M. Dequesnes, S. V. Rotkin, and N. R. Aluru, *Nanotechnology* **13**, 120–131 (2002).
- [7] J. M. Kinaret, T. Nord, and S. Viefers, *Appl. Phys. Lett.* **82**, 1287 (2003).
- [8] L. Maslov, *Nanotechnol.* **17**, 2475 (2006).
- [9] Yu. E. Lozovik, A. V. Minogin, and A. M. Popov, *Phys. Lett. A* **313**, 112 (2003).
- [10] Yu. E. Lozovik, A. V. Minogin, and A. M. Popov, *JETP Lett.* **77**, 631 (2003).
- [11] E. Bichoutskaia, A. M. Popov, M. I. Heggie, and Yu. E. Lozovik, *Fullerenes, Nanotubes, Carbon Nanostructures* **14**, 131 (2006).
- [12] A. V. Belikov, Yu. E. Lozovik, A. G. Nikolaev, and A. M. Popov, *Chem. Phys. Lett.* **385**, 72 (2004).
- [13] E. Bichoutskaia, A. M. Popov, M. I. Heggie, and Yu. E. Lozovik, *Phys. Rev. B* **73**, 045435 (2006).
- [14] P. R. Briddon and R. Jones, *phys. stat. sol. (b)* **217**, 131 (2000).
- [15] E. Bichoutskaia, A. M. Popov, A. El-Barbary, M. I. Heggie, and Yu. E. Lozovik, *Phys. Rev. B* **71**, 113403 (2005).
- [16] J. P. Perdew and Y. Wang, *Phys. Rev. B* **45**, 13244 (1992).
- [17] J. Kong, C. A. White, A. I. Krylov et al., *J. Comput. Chem.* **21**, 1532 (2000).
- [18] L. A. Girifalco, M. Hodak, and R. S. Lee, *Phys. Rev.* **62**, 13104 (2000).
- [19] D. E. Ellis, K. C. Mundimb, D. Fuksb et al., *Mater. Sci. Semicond. Process.* **3**, 123 (2000).
- [20] M. H. DeGroot and M. J. Schervish, *Probability and Statistics*, 3rd ed. (Addison-Wesley, 2002), 816 p.
- [21] I. M. Grace, S. W. Bailey, and C. J. Lambert, *Phys. Rev. B* **70**, 153405 (2004).
- [22] B. Gao, Y. F. Chen, M. S. Fuhrer, D. C. Glatli, and A. Bachtold, *Phys. Rev. Lett.* **95**, 196802 (2005).
- [23] G. S. Ivanchenko and N. G. Lebedev, *Phys. Solid State* **49**, 189 (2007).
- [24] E. Bichoutskaia, A. M. Popov, Yu. E. Lozovik, G. S. Ivanchenko, and N. G. Lebedev, *Phys. Lett. A* (2007), doi: 10.1016/j.physleta.2007.01.077, available online 21 February 2007.
- [25] E. Bichoutskaia, A. M. Popov, M. I. Heggie, and Yu. E. Lozovik, *Fullerenes, Nanotubes, Carbon Nanostructures* **14**, 215 (2006).
- [26] Yu. E. Lozovik and A. M. Popov, *Chem. Phys. Lett.* **328**, 355 (2000).
- [27] Yu. E. Lozovik, A. G. Nikolaev, and A. M. Popov, *Int. J. Nanotechnol.* **2**, 255 (2005).
- [28] Yu. E. Lozovik, A. G. Nikolaev, and A. M. Popov, *JETP* **103**, 447 (2006).
- [29] M. F. Yu, M. J. Dyer, G. D. Skidmore, H. W. Rohrs, X. K. Lu, K. D. Ausman, J. R. Von Ehr, and R. S. Ruoff, *Nanotechnology* **10**, 244 (1999).
- [30] S. C. Tsang, P. J. F. Harris, and M. L. H. Green, *Nature* **362**, 520 (1993).
- [31] K. El-Hami and K. Mitsushige, *Int. J. Nanoscience* **2**, 125 (2003).
- [32] Z. Liu and L. C. Qin, *Chem. Phys. Lett.* **408**, 75 (2005).